

# Preparation and Characterization of Fe/SiO<sub>2</sub> Nanoparticles Composite via Sol-Gel and Chemical Reduction Method

Van Thi Thanh Ho

Hochiminh City University of Natural Resources and Environment (HCMUNRE), Viet Nam

**Abstract**— *Fe/SiO<sub>2</sub> nanoparticles composite via sol-gel and chemical reduction method was studied in this work. We found that the Fe/SiO<sub>2</sub> nanocomposite is studied with various ratios between Fe and SiO<sub>2</sub>. We found that the Fe nanoparticles are distributed uniformly on the SiO<sub>2</sub> support, leading to enhance the surface area of Fe on the SiO<sub>2</sub> as well as improve the stability of Fe on SiO<sub>2</sub> compared to pure Fe. The results shows the surface area of Fe/SiO<sub>2</sub> is about of 50.108 m<sup>2</sup>/g, is much larger than the pure Fe (26 m<sup>2</sup>/g). The results of this work suggests that the way to synthesis Fe/SiO<sub>2</sub> nanocomposite with highly uniform distribution and surface area via sol-gel and chemical reduction method*

**Keywords**— *Fe/SiO<sub>2</sub>, sol-gel, Stober method, composite, nanoparticle.*

## I. INTRODUCTION

Fe NPs have shown a high chemical reduction rate on several kinds of contaminants, including toxic metal ions.[1-2] The properties of nanometer-sized magnetic iron particles have been investigated extensively by both experimental and theoretical analysis. On the one hand, these particles show promise for practical applications, such as catalysis, magnetic recording, magnetic fluids, and biomedical applications; on the other hand, their utility has been limited due to easy aggregation and uncontrolled oxidation. [3] The synthesis of Fe NPs with a uniform particle size distribution has been demonstrated using high-temperature thermolysis in oil-based reaction systems [4-5]. However, these reactions were considered harmful because of the involvement of toxic reagents and the high energy consumption. From the viewpoint of practical applications, any method to fabricate Fe NPs must take into account the susceptibility of Fe NPs to oxidation and aggregation owing to the magnetic interaction between the particles. Controlling the oxidation of Fe NPs is particularly important, as oxidation leads to degradation in their magnetic properties [6].

Since Fe NPs are oxidized rapidly in water and air, they exhibit a loss or decrease in magnetism and dispersibility in a biological environment. Therefore, preserving the

stability of Fe NPs is considered another challenge for biomedical applications. To prevent the oxidation of Fe NPs, the core-shell structures that are stable, biocompatible and hydrophilic were demonstrated using surface modifications with organic polymers of poly(acrylic acid) [7] poly(ethylene glycol) [8], dendrimers [9], chitosan [10-11] and silica (SiO<sub>2</sub>) layers. The SiO<sub>2</sub> shells provide an electrically-insulating layer that decreases energy loss and additionally prevents the possibility of a decrease in permeability due to Fe oxidation. Li et al. prepared  $\alpha$ -Fe nanoparticle/ordered mesoporous silica with the aid of a triblock copolymer using oxidation and reduction reactions [12]. Yang et al. formed Fe-core/SiO<sub>2</sub> shell nanoparticles using oleic acid and citric acid as the surface capping agents in an aqueous environment at room temperature. However, in this case, a 400°C reduction treatment was needed to obtain pure Fe/SiO<sub>2</sub> nanoparticles without FeO<sub>x</sub>, increasing the energy uptake.

The aim of this study was to prepare metallic Fe NPs on SiO<sub>2</sub> spheres like a nanoparticles composite to prevent iron oxidation and enhance the distribution of Fe on SiO<sub>2</sub> using a sol-gel process at low heat treatment conditions and the chemical reduction method. The Fe/SiO<sub>2</sub> nanoparticles composite are prepared with various compositions of Fe:SiO<sub>2</sub> to find out the good properties for the magnetic nanoparticles composite. The XRD, TEM, BET as well as the magnetic properties of the Fe/SiO<sub>2</sub> nanoparticles composite are characterized in detail in this work.

## II. EXPERIMENT

### 1. Materials

Tetraethylorthosilicate (TEOS), potassium borohydride (KBH<sub>4</sub>, 98%), anhydrous ferric chloride (FeCl<sub>3</sub>), potassium dichromate (K<sub>2</sub>Cr<sub>2</sub>O<sub>7</sub>), nitrogen (99,9%) and ethanol (99,5%) were all of analytic grade without further purifying. Deionized water was used throughout the study.

### 2. Preparation of iron nanoparticles coated with silica (Fe/SiO<sub>2</sub>)

Fe/SiO<sub>2</sub> nanoparticles composites were prepared by the sol-gel method combining with chemical reduction method without using any surfactant together with stabilizer. The

process includes two steps: the 1<sup>st</sup> step is the synthesis of SiO<sub>2</sub> nano size by the sol-gel method and the 2<sup>nd</sup> step is the preparation of Fe/SiO<sub>2</sub> by chemical reduction method using the KBH<sub>4</sub> as reductant agent at room temperature. The detail process is described as the **Fig. 1 and Fig. 2**.

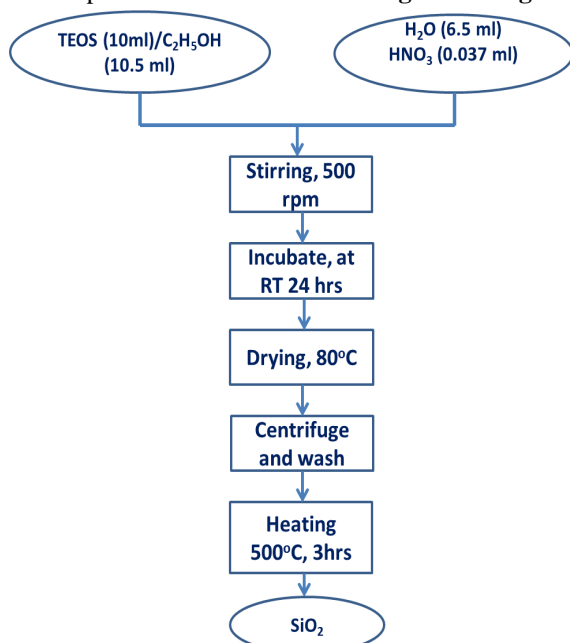


Fig.1: The 1<sup>st</sup> step to synthesis the SiO<sub>2</sub>

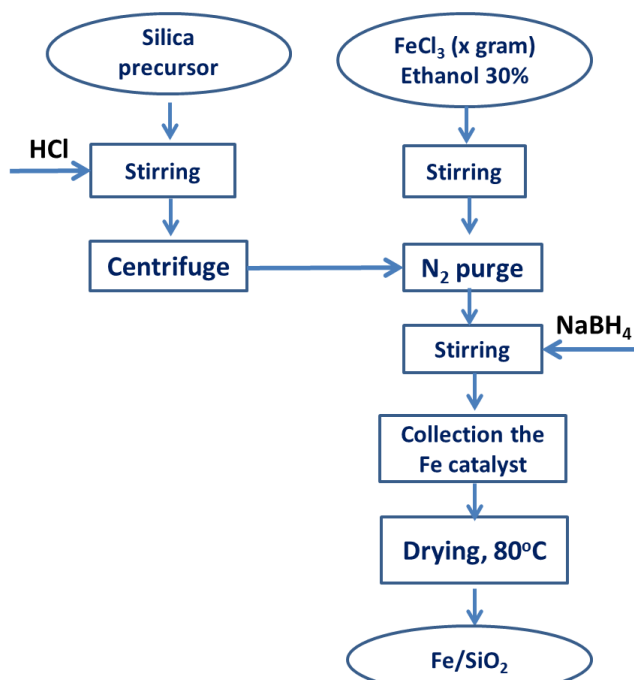


Fig.2: The 2<sup>nd</sup> step to synthesis the Fe/SiO<sub>2</sub> nanoparticle composite

### 3 Characterization of Fe/SiO<sub>2</sub>

X-ray diffraction (XRD) patterns of the specimens were recorded using an X-ray diffractometer (D8 Phaser, Bruker) equipped with a Cu K $\alpha$  radiation source (1.5406 Å) and nickel filter. Microstructure analysis was

performed with a transmission electron microscope (TEM, JEE 420-JEOL). The magnetic properties at room temperature were investigated using a vibrating sample magnetometer (MicroSense Easy VSM Software 9.13L). In addition, specific surface area of Fe/SiO<sub>2</sub> nanoparticles were measured by the Brumauer – Emmett – Teller (BET) method using Quantochrome NOVA 11.0.

### III. RESULT AND DISCUSSION

The Fe/SiO<sub>2</sub> nanocomposite is studied with various ratios between Fe and SiO<sub>2</sub> (see the table 1)

Table1: The samples of Fe/SiO<sub>2</sub> with various ratio of Fe:SiO<sub>2</sub>

No.	Sample	Fe:SiO <sub>2</sub>
1	F1S1	1:1
2	F2S1	2:1
3	F3S1	3:1

The color of Fe/SiO<sub>2</sub> nanocomposite could be observed clearly from the Figure 3. It can be seen that the F1S1 sample for the black color compared to other ratios, and the brown color of Fe/SiO<sub>2</sub> sample could be observed clearly for the sample with the Fe:SiO<sub>2</sub>=3:1 This result may be understood due to the high amount of Fe in the Fe/SiO<sub>2</sub> nanocomposite leading to oxidize easily to form the oxide Iron, resulting in the brown color formation. Therefore, the ratio of Fe:SiO<sub>2</sub> was selected to measure XRD, TEM, BET and Magnetic properties.

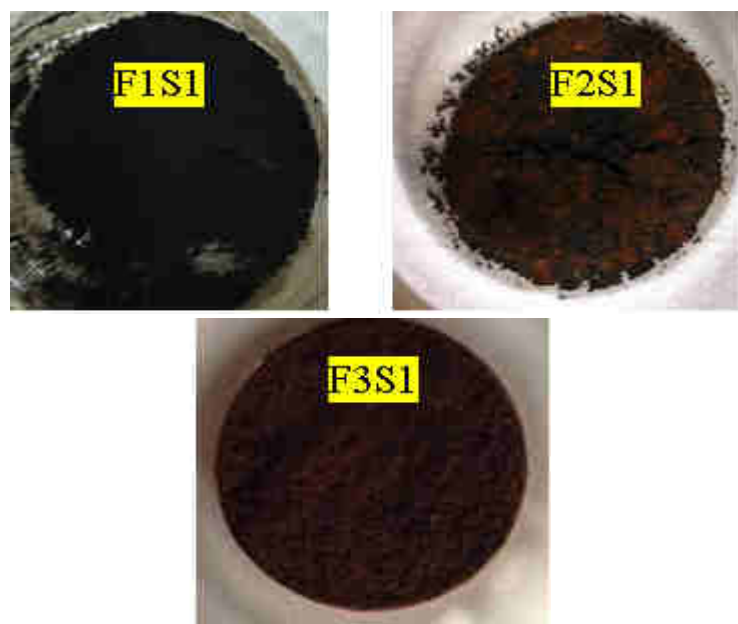
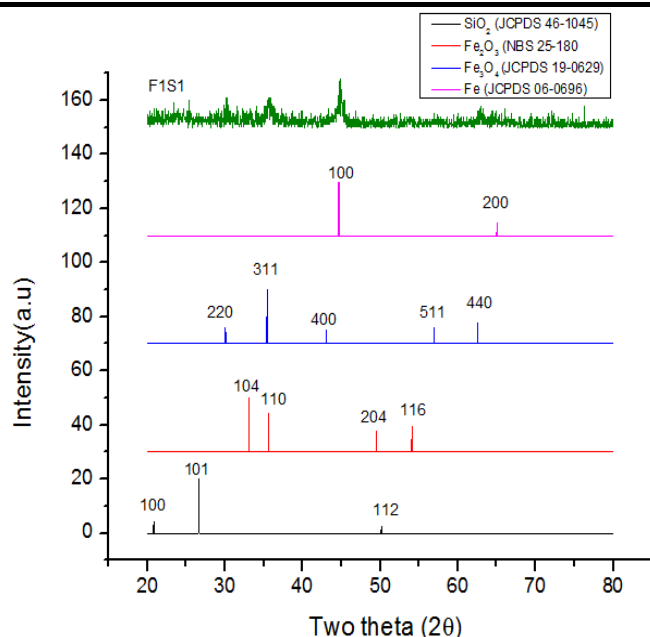



Fig.3: The color of Fe/SiO<sub>2</sub> with various ratio of Fe:SiO<sub>2</sub>



**Fig.4:** XRD pattern of the prepared Fe:SiO<sub>2</sub> =1:1 nanocomposite

**Figure 4** shows the XRD pattern of the prepared Fe:SiO<sub>2</sub> =1:1 nanocomposite. The XRD pattern demonstrated that SiO<sub>2</sub> were amorphous phase because of absencing of peaks corresponding to silica despite coating outside. Moreover, in **Fig. 4** we can see that the dominant Fe peak was observed for Fe:SiO<sub>2</sub> at  $2\theta=44.68^\circ$ , some weak peaks at  $35.5^\circ$  and  $30.1^\circ$  are corresponding to Fe<sub>3</sub>O<sub>4</sub> iron oxide. The diffraction peak at  $44.68^\circ$  is rather clearly due to the existing of  $\alpha$ -Fe particles (JCPDS card no. 06-0696).

The morphology of Fe/SiO<sub>2</sub> sample was examined by TEM measurement in **Figure 5**. It can be seen that the dark sphere was attributed to Fe and the gray shell can be attributed with SiO<sub>2</sub>. The Fe nanoparticles are distributed uniformly on the SiO<sub>2</sub> support, leading to enhance the surface area of Fe on the SiO<sub>2</sub> as well as improve the stability of Fe on SiO<sub>2</sub> compared to pure Fe.

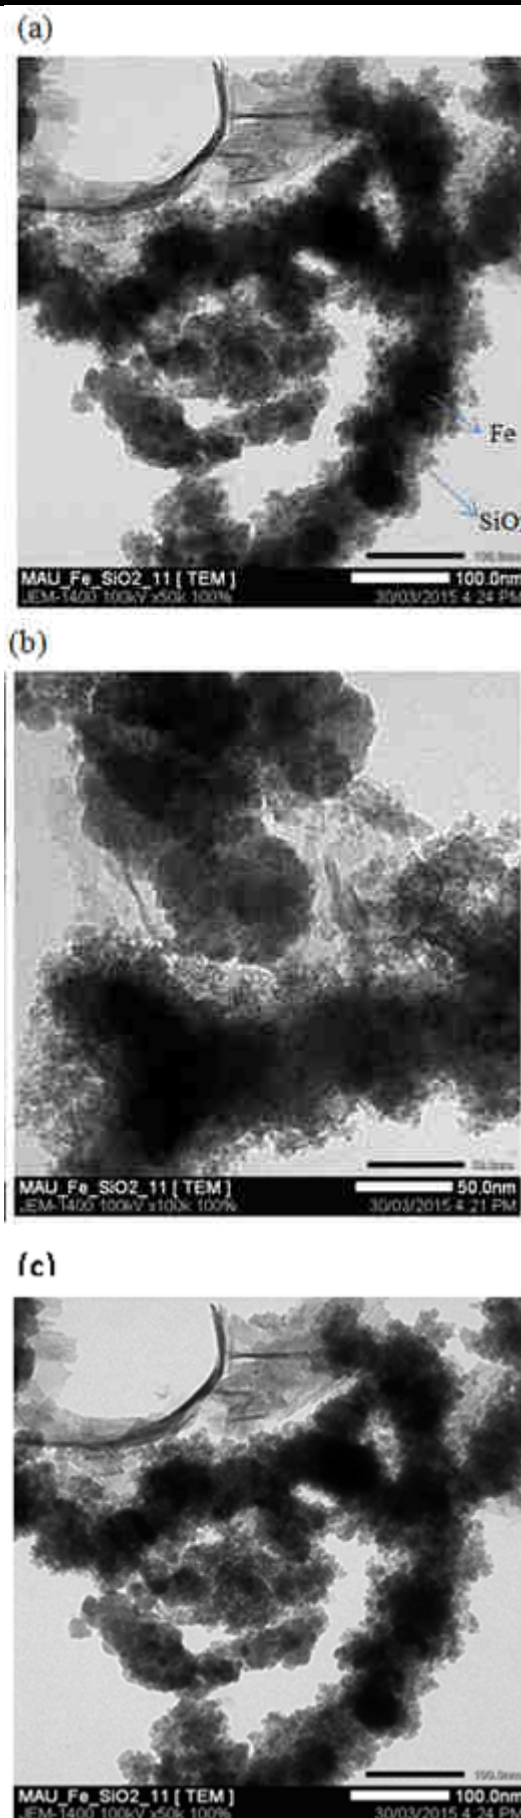

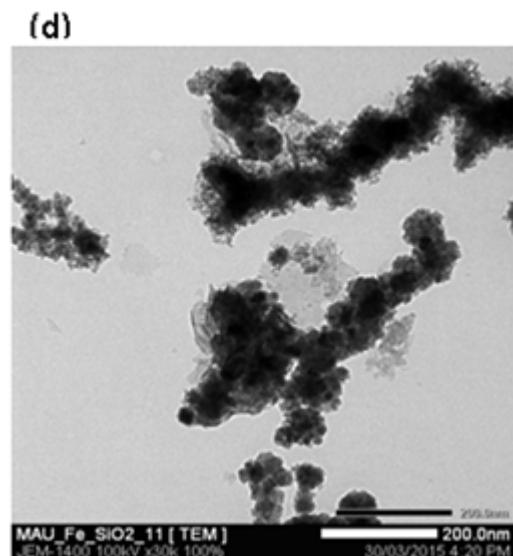


Fig.5: TEM measurement of Fe:SiO<sub>2</sub> sample, (a)- (d) overview and high resolution image.

The Fe:SiO<sub>2</sub> sample also was measure surface area by Brunauer–Emmett–Teller (BET) measurement. The results shows the surface area of Fe/SiO<sub>2</sub> is about 50.108 m<sup>2</sup>/g, is much larger than the pure Fe (25 m<sup>2</sup>/g) [13] from the previous research. This result could be concluded that the Fe is dispersed uniformly on the SiO<sub>2</sub> support.

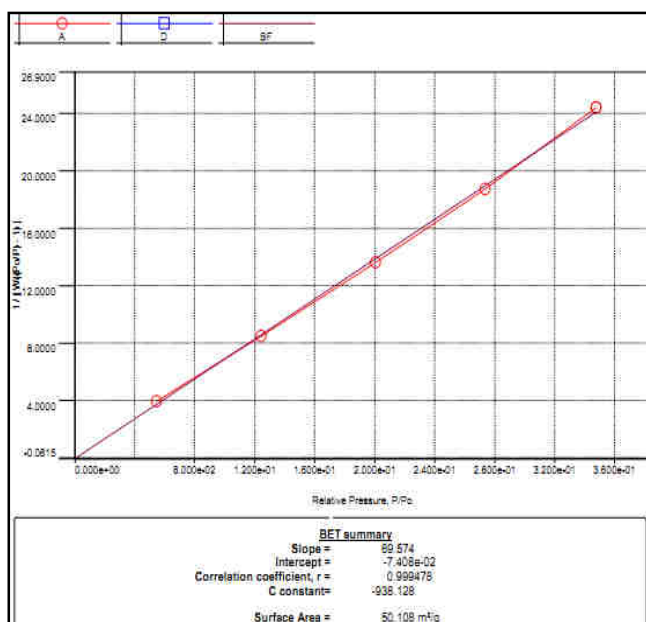


Fig.6: The BET surface area of Fe/SiO<sub>2</sub> (Fe:SiO<sub>2</sub>=1:1)

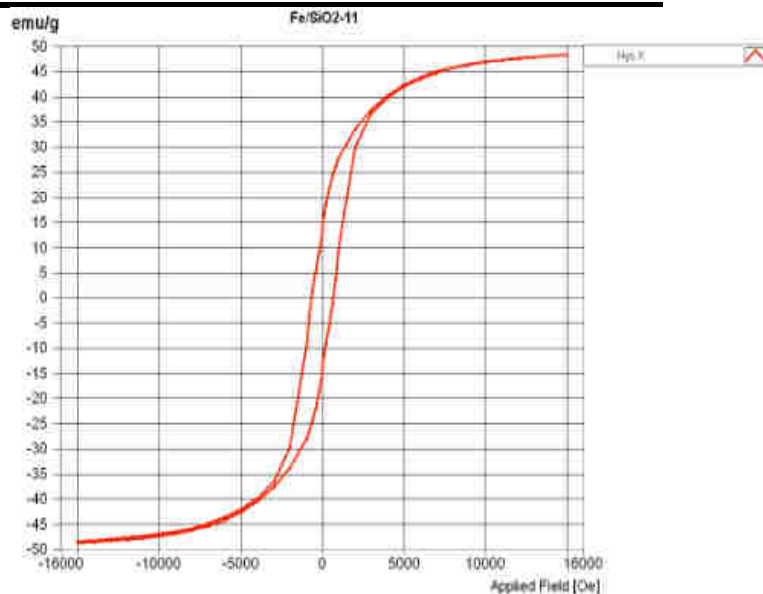


Fig.7: The magnetization hysteresis loops of Fe/SiO<sub>2</sub> with Fe:SiO<sub>2</sub>=1:1 (denoted sample F1S1) at room temperature

**Fig. 7** shows the magnetization hysteresis loops of Fe/SiO<sub>2</sub> (Fe:SiO<sub>2</sub>=1:1) sample at room temperature using a VSM in an applied field  $-1300 \text{ kA/m} \leq H \leq 1300 \text{ kA/m}$ . The coercivity ( $H_c$ ) value of the prepared Fe/SiO<sub>2</sub> (Fe:SiO<sub>2</sub>=1:1) was around  $H_c = 651.43 \text{ (Oe)} > 10 \text{ (Oe)}$ ,  $M_r = 13,713 \text{ (emu/g)}$ . The saturation magnetization value ( $M_s$ ) was about 48,517 (emu/g). Compared with bulk Fe ( $M_s = 220 \text{ emu/g}$ ), the  $M_s$  value of F1S1 sample was reduced. The magnetization discrepancy in magnetization value between bulk and our nanoparticles could be attributed to the small particle size effect. It is known that the saturation magnetization value of nanoparticles is smaller than that of corresponding bulk materials [14-18].

#### IV. CONCLUSION

In conclusion, Fe/SiO<sub>2</sub> nanoparticles were synthesized by sol-gel and chemical reduction method a simple method. The Fe/SiO<sub>2</sub> nanocomposite is studied with various ratios between Fe and SiO<sub>2</sub>. We found that the Fe nanoparticles are distributed uniformly on the SiO<sub>2</sub> support, leading to enhance the surface area of Fe on the SiO<sub>2</sub> as well as improve the stability of Fe on SiO<sub>2</sub> compared to pure Fe. The results shows the surface area of Fe/SiO<sub>2</sub> is about 50.108 m<sup>2</sup>/g, is much larger than the pure Fe (26 m<sup>2</sup>/g).

#### REFERENCES

- [1] S. M. Ponder, J. G. Darab, T. E. Mallouk, "Remediation of Cr(VI) and Pb(II) aqueous solutions using supported, nanoscale zero-valent iron" Environmental Science and Technology, vol. 34, no. 12, 2564-2569, 2000.
- [2] I. Dror, O. M. Jacov, A. Cortis, B. Berkowitz, Catalytic transformation of persistent contaminants



- using a new composite material based on nanosized zero-valent iron, *ACS Applied Materials and Interfaces*, vol. 4, No. 7, 3416-3423, 2012.
- [3] Liz-Marzan L. M, Mulvaney P. The assembly of coated nanocrystals, *J. Phys Chem B*, 2003, 107(30): 7312–7326.
- [4] Ling, T.; Xie, L.; Zhu, J.; Yu, H.; Ye, H.; Yu, R.; Cheng, Z.; Liu, L.; Liu, L.; Yang, G.; et al. Icosahedral face-centered cubic Fe nanoparticles: Facile synthesis and characterization with aberration-corrected TEM. *Nano Lett.* 2009, 9, 1572–1576.
- [5] Yang, T.I.; Brown, R.N.C.; Kempel, L.C.; Kofinas, P. Controlled synthesis of core-shell iron-silica nanoparticles and their magneto-dielectric properties in polymer composites. *Nanotechnology* 2011, 22, 105601–105608.
- [6] Kohara, K.; Yamamoto, S.; Seinberg, L.; Murakami, T.; Tsujimoto, M.; Ogaw, T.; Kurata, H.; Kageyama, H.; Takano, M. Carboxylated SiO<sub>2</sub>-coated  $\alpha$ -Fe nanoparticles: Towards a versatile platform for biomedical, applications. *Chem. Commun.* 2013, 49, 2563–2565.
- [7] Zhang, T.; Ge, J.; Hu, Y.; Yin, Y. A general approach for transferring hydrophobic nanocrystals into water. *Nano Lett.* 2007, 7, 3203–3207.
- [8] Hervé, K.; Douziech-Eyrolles, L.; Munnier, E.; Cohen-Jonathan, S.; Soucé, M.; Marchais, H.; Limelette, P.; Warmont, F.; Saboungi, M.L.; Dubois, P.; et al. The development of stable aqueous suspensions of PEGylated SPIONs for biomedical applications. *Nanotechnology* 2008, 19.
- [9] Zhu, R.; Jiang, W.; Pu, Y.; Luo, K.; Wu, Y.; He, B.; Gu, Z. Functionalization of magnetic nanoparticles with peptide dendrimers. *J. Mater. Chem.* 2011, 21, 5464–5474.
- [10] Zhua, A.; Yuan, L.; Liao, T. Suspension of Fe<sub>3</sub>O<sub>4</sub> nanoparticles stabilized by chitosan and *o*-carboxymethylchitosan. *Int. J. Pharm.* 2008, 350, 361–368. [CrossRef] [PubMed]
- [11] Li, G.Y.; Jiang, Y.R.; Huang, K.L.; Ding, P.; Chen, J. Preparation and properties of magnetic Fe<sub>3</sub>O<sub>4</sub>-chitosan nanoparticles. *J. Alloys Compd.* 2008, 466, 451–456.
- [12] Li, J.; Li, H.; Zhu, Y.; Hao, Y.; Sun, X.; Wang, L. Dual roles of amphiphilic triblock copolymer P123 in synthesis of  $\alpha$ -Fe nanoparticle/ordered mesoporous silica composites. *Appl. Surf. Sci.* 2011, 258, 657–661.
- [13] R. Yuvakkumar et al.. “Preparation and characterization of zero valent iron nanoparticles”, *Digest Journal of Nanomaterials and Biostructurer*, vol.6 (4), pp. 1771-1776, 2011).
- [14] X. Q. Li, W. X. Zhang, Iron nanoparticles: the core-shell structure and unique properties for Ni(II) sequestration, *Langmuir*, vol. 22, no. 10, 4638-4642, 2006
- [15] A. Alqudami, N. A. Alhemiary, S. Munassar, Removal of Pb(II) and Cd(II) ions from water by Fe and Ag nanoparticles prepared using electro-exploding wire technique, *Environmental Science and Pollution Research*, vol. 19, 2832-2841, 2012.
- [16] S. M. Ponder, J. G. Darab, T. E. Mallouk, Remediation of Cr(VI) and Pb(II) aqueous solutions using supported, nanoscale zero-valent iron” *Environmental Science and Technology*, vol. 34, no. 12, 2564-2569, 2000.
- [17] I. Dror, O. M. Jacov, A. Cortis, B. Berkowitz, Catalytic transformation of persistent contaminants using a new composite material based on nanosized zero-valent iron, *ACS Applied Materials and Interfaces*, vol. 4, no. 7, 3416-3423, 2012.
- [18] Li, X. Q; Elliott, D. W; Zhang, W. X. Zero-valent iron nanoparticles for abatement of environment pollutants: materials and engineering aspects, *Crit. Rev. Solid State Mater. Sci* 2006, 31 (4), 111-122