

A New Possibility of Dynamical Study on Solid State Ionic Materials by Inelastic Neutron Scattering

M. Nakamura^{1*}, K. Nakajima¹, Y. Inamura¹, S. Ohira-Kawamura¹, T. Kikuchi¹, T. Otomo^{1,2} and M. Arai¹

¹ Materials and Life Science Division, J-PARC Center, Tokai, Ibaraki, 319-1195, Japan

² Institute of Materials Structure Science, High energy Accelerator Research Organization (KEK), Tsukuba, Ibaraki 305-0801, Japan

ARTICLE INFO

Article history:

Received 30 September 2010

Received in Revised form 25 October 2010

Accepted 26 October 2010

Keywords:

Inelastic neutron scattering

J-PARC

Pulsed neutron source

Pulsed neutron techniques

Solid state ionic materials

ABSTRACT

A new technique of inelastic neutron scattering measurement utilizing the multiple incident energies is applied to the dynamical study of vitreous silica. A wide variety of extracted information from a series of two-dimensional maps of dynamical structure factor with multiple different incident energies are greatly valuable. The applicability and its expected contribution of new experimental technique into the further progress of scientific activities in solid state ionic materials are discussed.

© 2010 Atom Indonesia. All rights reserved

INTRODUCTION

Neutron scattering measurements have played an important role in the study of solid state ionic materials. For example, diffraction measurement provided a lot of structural information, and also quasi-elastic neutron scattering (QENS) measurement revealed the diffusion mechanism of mobile ions. On the other hand, inelastic neutron scattering (INS) measurement was not a major experimental method in the dynamical study of solid state ionic materials due to the low flux of neutron beam. However, the MW-class pulsed neutron source such a Japan Proton Accelerator Research Complex (J-PARC) may completely change the situation. The INS measurement with pulsed neutron source is able to provide a new stage for the dynamical study of solid state ionic materials through a two-dimensional map of dynamical structure factor $S(Q, E)$ over wide Q - E range. We can easily extract a series of constant Q or E slices and also the integration over the arbitrary Q or E ranges from $S(Q, E)$ map. In fact, our previous works on superionic conductors using INS measurement with pulsed neutron source have given new insight into the origin of ionic conductivity in the solid state [1-4]. As an example, the comparison of low-energy dynamics between superionic conducting glass $(\text{AgI})_{0.5}(\text{AgPO}_3)_{0.5}$ and insulator glass AgPO_3 was

illustrated in Fig. 1. The low-energy intensity (below 5 meV) of superionic conducting glass is much larger than that of insulator glass as shown in Fig. 1(a). One of the greatest benefits of INS measurement is that we can discuss the Q -dependent features of inelastic signal. Figure 1(b) shows the constant- E slices ($1 \text{ meV} < E < 3 \text{ meV}$) for both $(\text{AgI})_{0.5}(\text{AgPO}_3)_{0.5}$ and AgPO_3 , which clearly indicates that an excess low-energy intensity of superionic conducting glass is caused by a unique dynamics in the Q range beyond around 2 \AA^{-1} .

Furthermore, we have succeeded in experimentally demonstrating that a series of two-dimensional maps of $S(Q, E)$ with multiple incident energies can be simultaneously obtained by one measurement (multi- E_i measurement). The first demonstration of multi- E_i measurement was conducted on the observation of magnetic excitations in the spin-Peierls compound CuGeO_3 single crystals using a Fermi chopper spectrometer 4SEASONS at J-PARC [5]. The multi- E_i measurement reduces the dead time of time-of-flight (TOF) measurement, and thus, it markedly increases the INS measurement efficiency [6]. Thus a new experimental technique is also markedly powerful for the dynamical study of *isotropic* materials, such as glass, liquid, and polycrystalline materials, which are typical form of solid state ionic materials. Accordingly, we are now ready for the breakthrough of scientific activities on the solid state ionic materials by making full use of both high neutron

* Corresponding author.

E-mail address: mitsutaka.nakamura@j-parc.jp (M. Nakamura)

flux realized at J-PARC and novel experimental technique. In this study, multi-Ei measurement is applied to the dynamical study of vitreous silica (ν -SiO₂) which is the most famous *isotropic* material, and the availability of multi-Ei measurement in the dynamical study of solid state ionic materials is validated.

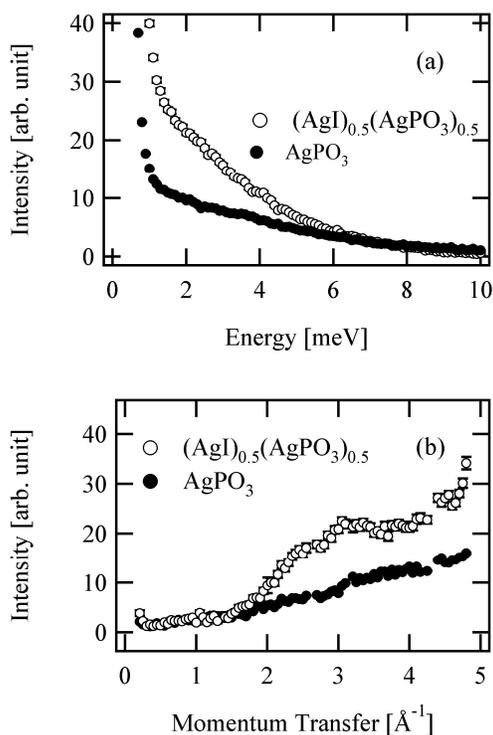


Fig. 1. Comparison of inelastic scattering between superionic conducting glass (AgI)_{0.5}(AgPO₃)_{0.5} and insulator glass AgPO₃ [1]. All data were measured by MARI spectrometer at the ISIS facility, UK, and the environmental temperature was room temperature; (a) the energy dependence of $S(Q,E)$ obtained by the total integration along the Q direction, and (b) the constant- E slices of $S(Q,E)$ integrated between 1 meV and 3 meV.

EXPERIMENTAL METHODS

The multi-Ei measurement of ν -SiO₂ was carried out on the AMATERAS spectrometer at the J-PARC. AMATERAS is a direct geometry disk-chopper spectrometer and designed for wide momentum-energy space measurement with high resolution and high flux [7]. The incident beam flux and resolutions of AMATERAS are flexibly tuned by changing the parameters of multiple disk choppers, such as the rotation speed and slit size. The moderator—sample distance (L_1), the sample—detector distance (L_2), and the monochromating chopper—sample distance (L_3) are 30, 4, 1.6 m, respectively. $\phi 25.4$ mm \times 2.9 m position-sensitive detectors (PSDs) are cylindrically arranged with a radius of L_2 around the sample. The

data are collected using a newly developed event-mode data acquisition system, where each neutron captured by PSD is tagged with time stamp and stored over the source period (40 ms in J-PARC) event by event [8,9]. This data acquisition system enables users to freely pick up and reedit the TOF data sets based on the tag information. Several TOF data sets are independently analyzed for each inelastic scattering process in multi-Ei measurement.

Incident energy is arbitrarily selected by tuning the phase delay of monochromating chopper. Usual monochromating chopper frequency (100–600 Hz) is greatly larger than the accelerator frequency of pulsed neutron source (25 Hz in J-PARC). It follows that chopper window is opening many times within 1-frame of accelerator period (40 ms in J-PARC). Accordingly, multiple incident energy neutrons can pass through a monochromating chopper. A general formula of the n th incident wavelength $\lambda_i(n)$ [Å] selected by a monochromating chopper [6] is

$$\lambda_i(n) = \lambda_i(1) + \frac{3956(n-1)}{(L_1 - L_3)f}, \quad (1)$$

where $\lambda_i(1)$ [Å] is the shortest wavelength among the multiple incident neutrons, f [Hz] the frequency of monochromating chopper. The unit of L_1 and L_3 in Equation (1) is meter. Incident energy E_i [meV] is calculated by a following relation with incident wavelength λ_i [Å]

$$E_i = \frac{81.81}{\lambda_i^2}. \quad (2)$$

In this experiment, monochromating chopper frequency is 150 Hz, and selected incident energies are 94.1, 23.6, 10.5, and 5.9 meV. The incident beam size was 20 mm (width) \times 30 mm (height). The sample of ν -SiO₂ was columnar form. Its diameter was 9 mm and its length was 80 mm. The measurement was carried out at room temperature.

RESULTS AND DISCUSSION

Figure 2 shows the TOF spectrum of ν -SiO₂, which accumulate the data from all the detector pixels in the horizontal plane. We can observe several elastic peaks at every ~ 7980 μ s, which corresponds to the rotation period of the monochromating chopper at the detector position, i.e., $1/f$ [Hz] $\times (L_1 + L_2) / (L_1 - L_3) \times 10^6$ μ s. These peaks correspond to $E_i = 94.1, 23.6, 10.5,$ and 5.9 meV in order of arrival time. Inelastic processes

for multiple E_i 's are independently analyzed, and thus, we obtained four different $S(Q,E)$ maps from one data set as shown in Fig. 3. One can see an overall feature of the excitations from the data with high E_i , while the data with small E_i gives precise information at low-energy region. In other words, the $S(Q,E)$ map with high E_i and that with low E_i have a zoom-in/out relation each other. Instrumental noise and background brought about several streaks at $E \sim 8$ meV in Fig. 3(c) and $E \sim 2$ meV in Fig. 3(d), where now we have already succeeded to suppress these fake signals.

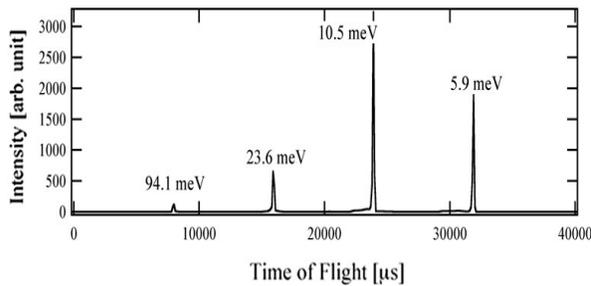


Fig. 2. TOF spectrum of ν -SiO₂. Data were collected using detector pixels positioned in the horizontal plane. The monochromating chopper frequency was 150 Hz, and phase delay was tuned to the incident energy of 23.6 meV. Other incident neutrons with different energies were also concomitantly delivered to the sample.

Until now, enormous works have been done on both the structure and the dynamical properties of ν -SiO₂, which have been the subject of many review articles (for example, see [10]). A lot of valuable information can be extracted from the respective $S(Q,E)$ maps shown in Fig. 3. Some results are given in Fig. 4, and thus, we can examine the quality of new obtained data as compared with the results published in the literature. Fig. 4(a) shows the constant- E slices of $S(Q,E)$ map with $E_i = 94.1$ meV, where the selected energy transfers are 15, 30, 45, 60 meV. Each intensity is subtracted by constant background and then divided by Q^2 . It is obvious that there exists the dispersive behavior up to 60 meV despite the lack of structural periodicity. This result is consistent with previous works [11,12]. The E dependence of $S(Q,E)$ with $E_i = 23.6$ meV, obtained by the total integration over Q , is plotted in Fig. 4(b). The so-called Boson Peak is clearly observed. More detailed investigations on the Q dependence of Boson Peak is also feasible from the data with middle E_i 's, such as $E_i = 23.6$ or 10.5 meV. Elastic parts of $S(Q,E)$ with both $E_i = 94.1$ meV and $E_i = 5.9$ meV are shown in Fig. 4(c) and Fig. 4(d), respectively. For both spectra, the first sharp diffraction peak (FSDP) is observed around 1.5 \AA^{-1} . Fig. 4(c) gives us the spectral features over

wide Q range, while Fig. 4(d) represents finer spectral features in the limited Q region. The appearance of a weak shoulder below 1.0 \AA^{-1} can be seen in Fig. 4(d).

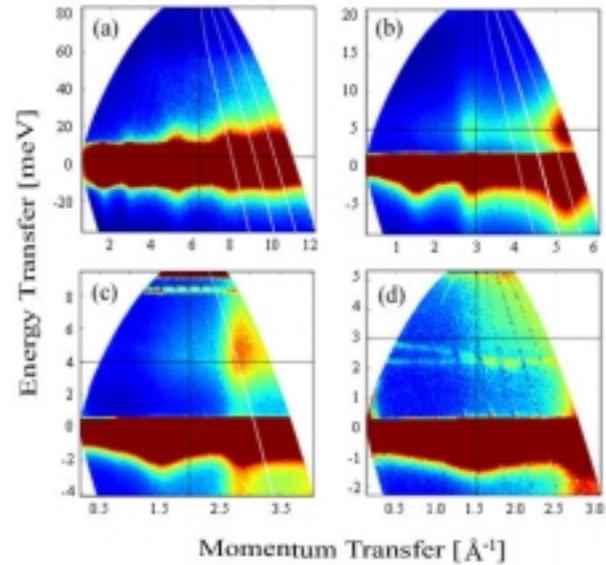


Fig. 3. Simultaneous observation of multiple two-dimensional $S(Q,E)$ maps for ν -SiO₂ by one measurement. The horizontal axis shows the momentum transfer and the vertical axis shows the energy transfer. The incident energies are (a) 94.1, (b) 23.6, (c) 10.5, and (d) 5.9 meV.

Next, let us discuss the availability of multi- E_i measurement for the study of solid state ionic materials. The data with high E_i covers the wide Q range, from which we can estimate the Debye-Waller factor and averaged mean-square displacement [13]. The temperature dependence or composition dependence of averaged mean-square displacement should yield valuable information on the mechanism of ionic conductivity. In addition, higher incident energy measurement more than 100 meV may indicate some dynamical changes in connection with the activation energy of mobile ions which is usually in the range between 0.1 eV and 1 eV. On the other hand, the data with small E_i provides more detailed information in the lower Q range. Detailed investigation on the Q dependence of low-energy excitation in the solid state ionic materials will promote better understanding of peculiar dynamical properties presented by the previous experiments at the ISIS [1-4]. It is well known that the structure factor of superionic conducting glass exhibits a strong and relatively sharp diffraction peak at anomalously low values of Q ($0.6 < Q < 0.8 \text{ \AA}^{-1}$) [14,15]. The data with smaller E_i (< 10 meV) will enable to develop the dynamical study of this anomalous prepeak.

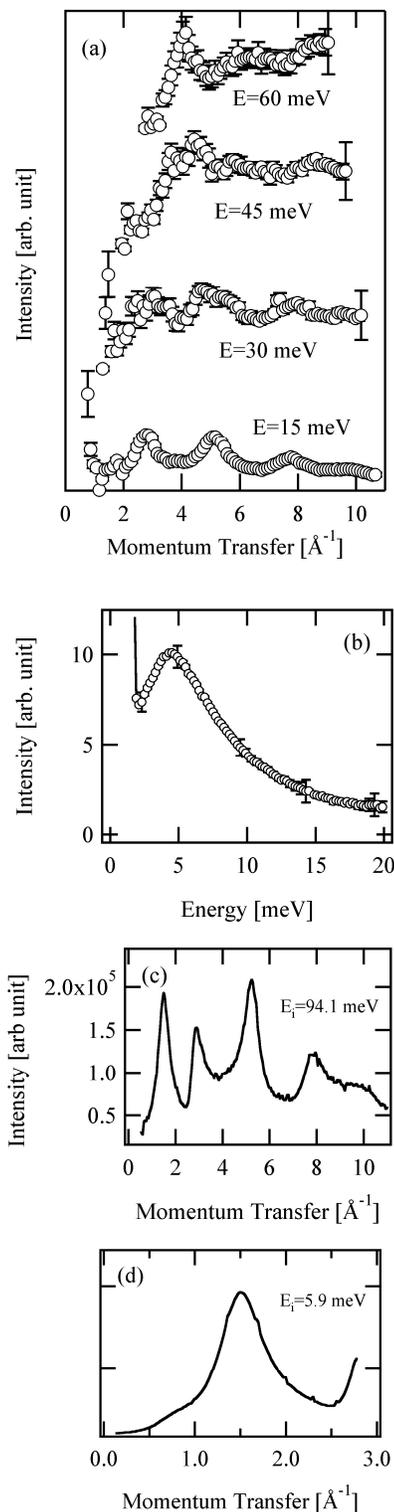


Fig. 4. Several plots extracted from the multiple $S(Q,E)$ maps in Fig. 3. (a) The constant- E slices of the $S(Q,E)$ with $E_f=94.1$ meV for $E=15, 30, 45, 60$ meV. (b) The energy dependence of the $S(Q,E)$ with $E_f=23.6$ meV obtained by total integration along the Q direction. The so-called Boson Peak is observed around 5 meV. The elastic parts of the $S(Q,E)$ with (c) $E_f=94.1$ meV and (d) $E_f=5.9$ meV. The first sharp diffraction peak is observed around 1.5\AA^{-1} .

For the study of diffusion mechanism of mobile ions in solid state ionic materials, AMATERAS spectrometer at J-PARC also enables the QENS measurement with high resolution ($\Delta E < 10 \mu\text{eV}$) by the combination of multiple fast disk choppers [7]. The continuous Q dependences of QENS spectra can be available at the AMATERAS through a two-dimensional $S(Q,E)$ map. Furthermore, AMATERAS was designed to facilitate the “multi-Ei QENS measurement” using multiple incident energies [6]. This experimental technique should be also greatly useful for the diffusion study of solid state ionic materials.

We would like to emphasize again that a wide variety of information can be extracted from only one data set of multi-Ei measurement. The highly efficient INS measurement by a new technique should enhance the research activities on the solid state ionic materials. The beam power of the J-PARC accelerator was 120 kW at the time we performed this study. Increasing the beam power to final goal (1 MW) is scheduled in accordance with the project plan. The combination of multi-Ei measurement and final beam power of 1 MW at J-PARC will yield an unrivaled ability in various research fields of condensed matter physics.

CONCLUSIONS

In this paper, we have experimentally demonstrated that the multi-Ei measurement using a chopper spectrometer at the pulsed neutron source is markedly powerful for the dynamical study of a typical *isotropic* material, vitreous SiO_2 . The multiple two-dimensional $S(Q,E)$ maps are simultaneously obtained by one measurement. The full picture of dynamical properties, which include the overall feature over wide Q - E space and the precise information in the low Q - E region, is promptly captured. These results confirm that the multi-Ei measurement has the possibility to greatly advance the dynamical study of solid state ionic materials which are usually isotropic form (glassy or polycrystalline one).

ACKNOWLEDGMENTS

We are grateful to E. Kartini for the sample preparation of $(\text{AgI})_{0.5}(\text{AgPO}_3)_{0.5}$ and AgPO_3 glasses. We are also grateful to the technical support team of J-PARC Center for their help in the experiment. This work was supported by a Grant-in-Aid for Specially Promoted Research (No. 17001001) from the Ministry of Education, Culture, Sports, Science and Technology of Japan,

and a Grant-in-Aid for Scientific Research C (No. 20612016) from the Japan Society for the Promotion of Science.

REFERENCES

1. M. Nakamura, M. Arai, Y. Inamura and E. Kartini, *J. Phys. Soc. Jpn.* **79** (2010) Suppl. A 122.
2. E. Kartini, M. Nakamura, M. Arai, Y. Inamura, J. W. Taylor, and M. Russina, *Solid State Ionics* **180** (2009) 506.
3. M. Arai, H. Iwase, M. Nakamura, T. Otomo, E. Kartini, K. Itoh, S.J. Levett, and S.M. Bennington, *AIP Conf. Proc.* **832** (2006) 299.
4. M. Nakamura, M. Arai, E. Kartini, J. W. Taylor, and M. Russina, *AIP Conf. Proc.* **832** (2006) 504.
5. M. Nakamura, R. Kajimoto, Y. Inamura, F. Mizuno, M. Fujita, T. Yokoo and M. Arai, *J. Phys. Soc. Jpn.* **78** (2009) 093002.
6. M. Nakamura, K. Nakajima, R. Kajimoto, and M. Arai, *J. Neutron Res.* **15** (2007) 31.
7. K. Nakajima, M. Nakamura, R. Kajimoto, T. Osakabe, K. Kakurai, M. Matsuda, N. Metoki, S. Wakimoto, T. J. Sato, S. Itoh, M. Arai, K. Yoshida, and K. Niita, *J. Neutron Res.* **15** (2007) 13.
8. S. Satoh, S. Muto, N. Kaneko, T. Uchida, M. Tanaka, Y. Yasu, K. Nakayoshi, E. Inoue, H. Sendai, T. Nakatani, and T. Otomo, *Nucl. Instrum. Methods Phys. Res., Sect. A* **600** (2009) 103.
9. K. Nakayoshi, Y. Yasu, E. Inoue, H. Sendai, S. Satoh, S. Muto, N. Kaneko, T. Otomo, T. Nakatani and T. Uchida, *Nucl. Instrum. Methods Phys. Res., Sect. A* **600**, (2009) 173.
10. T. Nakayama, *Rep. Prog. Phys.* **65** (2002) 1195.
11. M. Arai, Y. Inamura and T. Otomo, *Philos. Mag. B* **79** (1999) 1733.
12. M. Arai, Y. Inamura, T. Otomo, N. Kitamura, S. M. Bennington, and A. C. Hannon, *Physica B* **263-264** (1999) 268.
13. M. Nakamura, M. Arai, Y. Inamura, T. Otomo, and S. M. Bennington, *Phys. Rev. B* **66** (2002) 024203.
14. L. Börjesson, L. M. Torell, U. Dahlborg, and W. S. Howells, *Phys. Rev. B* **39** (1989) 3404.
15. E. Kartini, M. F. Collins, T. Priyanto, M. Yusuf, N. Indayaningsih, E. C. Svensson, and S. J. Kennedy, *Phys. Rev. B* **61** (2000) 1036.