

ORGANOMETALLIC $[\text{Fe}_3\text{O}(\text{OCC}_6\text{H}_5)_6(\text{H}_2\text{O})_3](\text{NO}_3)$ AS INTERCALANT OF BENTONITE

Hasja Paluta Utami^{1,*} and Donny Marihot Siburian¹

¹Departement of Chemistry, Faculty of Mathematic and Natural Sciences, Sriwijaya University

*Corresponding Author e-mail : hasjapaluta8@gmail.com

ABSTRACT

Intercalation of organometallic compounds $[\text{Fe}_3\text{O}(\text{OCC}_6\text{H}_5)_6(\text{H}_2\text{O})](\text{NO}_3) \cdot n\text{H}_2\text{O}$ on bentonite by weight ratio of bentonite:organometallic (1 : 1); (1 : 2); (1 : 3); and (1 : 4) has been carried out. The intercalation bentonite was characterized using FT-IR spectrophotometer, XRD and XRF analyses. Characterization using FT-IR spectrophotometer showed higher intensity of peak wavenumber at 470.6 cm^{-1} for $\text{Fe}_3\text{-O}$ vibration on the ratio (1 : 3). While XRD characterization showed the shift of diffraction angle of 2θ was 5.2° and has basal spacing of 16.8 Å. In the XRF characterization, the intercalation process of organometallic compounds $[\text{Fe}_3\text{O}(\text{OCC}_6\text{H}_5)_6(\text{H}_2\text{O})](\text{NO}_3) \cdot n\text{H}_2\text{O}$ on bentonite was occurred optimally with percentage of metal oxide reached 71.75 %.

Keywords: intercalation, bentonite, organometallic, $[\text{Fe}_3\text{O}(\text{OCC}_6\text{H}_5)_6(\text{H}_2\text{O})](\text{NO}_3) \cdot n\text{H}_2\text{O}$.

INTRODUCTION

Bentonite is a layered material contain inorganic minerals who can find easily in natural (Abderrazek et al, 2016). Bentonite are used as adsorbent, catalyst, ion exchange, and various industrial applications (Santos et al, 2016). In the application of bentonite as adsorbent have some weakness, due to impurities of some minerals that can make the adsorption is not optimal. Therefore, to optimize the adsorption process then bentonite should be activated. The process activation of bentonite is intended to separate the impurities naturally from bentonite. In general, there are two step of activation process for activation including physically and chemically processes. On physical processes is needed to combustion in a high temperature causes water molecules from crystal and other inorganic constituents, so that two cluster OH who bonded each other, they have to detach one water molecule (Scoonheydt et al, 2008), while on chemical processes by using acid mineral such as sulfuric acid is intended to omit the metals that be found in bentonite and banded in ion H^+ which is originated from acid. therefore the layer who as an insertion entry will be larger. The modification of bentonite is expected to produce bentonite which can be conducted by insertion of molecules, compounds, and organic/inorganic complexes.

The research of layer materials intercalation including bentonite using metal oxides shows distance between layer is a little small (Yang et al, 2005). Thus higher compound with positive charge is needed as intercalant of bentonite. This research was conducted an intercalation process of bentonite using a organometallic compound as insertion. Organometallic compound $[\text{Fe}_3\text{O}(\text{OCC}_6\text{H}_5)_6(\text{H}_2\text{O})](\text{NO}_3) \cdot n\text{H}_2\text{O}$ have advantage such as high reactivity, high cation size, and also easy to synthesis. In this research, various weight of organometallic compound has been used to know the optimal intercalation process. The ratio of bentonite:organometallic complex was

(1:1); (1:2); (1:3); and (1:4). Product of insertion was characterized by spectrophotometer FT-IR, XRD, and XRF analyses in order to know the optimal insertion process.

EXPERIMENTAL SECTION

Materials

Natural bentonite was obtained from Jambi Province, Indonesia. Sulfuric acid, Iron(III) nitrate, sodium benzoate, and sodium hydroxide was obtained from Merck and directly used after purchased. Deionized water was supplied from Purite®.

Preparation of Bentonite (Ozcan, 2016)

The nature bentonite is prepared by physically and chemically processes. 100 g of natural bentonite was heated using furnace at 400 °C for two hours then the material was kept at room temperature over night. The bentonite then was acidified using sulfuric acid for two hours. Bentonite after treatment was characterized using FT-IR spectrophotometer, XRD, and XRF.

Synthesis of Organometallic Compounds

$[\text{Fe}_3\text{O}(\text{OCC}_6\text{H}_5)_6(\text{H}_2\text{O})](\text{NO}_3) \cdot n\text{H}_2\text{O}$ (Uchida et al, 2008)

Synthesis of organometallic compounds was carried out by mixing a 32 g of iron(III)nitrate that has been dissolved in 100 mL of water. In the solution was added 24 g sodium benzoate and the mixtures were stirred by magnetic stirrer for 15 minutes. The brown orange solution will be formed, filtered, washed by water to obtain $[\text{Fe}_3\text{O}(\text{OCC}_6\text{H}_5)_6(\text{H}_2\text{O})](\text{NO}_3) \cdot n\text{H}_2\text{O}$. Organometallic compound was characterized using FT-IR spectrophotometer.

Intercalation of Bentonite with Organometallic Compound $[\text{Fe}_3\text{O}(\text{OCC}_6\text{H}_5)_6(\text{H}_2\text{O})](\text{NO}_3) \cdot n\text{H}_2\text{O}$ (Gil et al, 2009)

Bentonite was mixed with 200 mL water to form white suspension (reactan A). Organometallic compound as intercalant compound was prepared by adding 100 mL sodium hydroxide (NaOH) 1 M into 15 g of organometallic compound (reactan B). Reactan A and B was mixed and the mixtures was

Article History

Submitted: 23 July 2016

Accepted: 5 August 2016

DOI: 10.26554/sti.2016.1.1.20-24

refluxed with gentle stirring for 24 hours at room temperature under nitrogen gas. The product intercalation of bentonite with organometallic compounds was washed with water and dried at 90 °C. In order to know the optimum intercalation process, the ratio of bentonite:organometallic compound was applied (1 : 1); (1 : 2); (1 : 3); and (1 : 4). The bentonite intercalated organometallic compounds were characterized using FT-IR spectrophotometer, XRD and XRF analysis.

RESULTS AND DISCUSSION

Synthesis and Characterization of Organometallic Compounds $[\text{Fe}_3\text{O}(\text{OOCCH}_2\text{C}_6\text{H}_5)_6(\text{H}_2\text{O})_3](\text{NO}_3)\cdot n\text{H}_2\text{O}$

Synthesis of organometallic compounds $[\text{Fe}_3\text{O}(\text{OOCCH}_2\text{C}_6\text{H}_5)_6(\text{H}_2\text{O})_3](\text{NO}_3)\cdot n\text{H}_2\text{O}$ was carried out under air conditions without protection of an inert gas, which has different from almost synthesis of organometallic complexes (Szafran et al, 1991). Organometallic compounds $[\text{Fe}_3\text{O}(\text{OOCCH}_2\text{C}_6\text{H}_5)_6(\text{H}_2\text{O})_3](\text{NO}_3)\cdot n\text{H}_2\text{O}$ has light brown crystals. The organometallic compounds were then characterized using FT-IR spectrophotometer aimed to identifying functional groups showed in Figure 1.

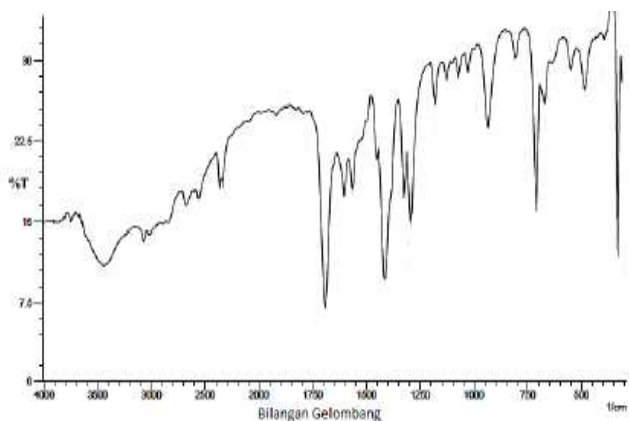


Figure 1. FT-IR Spectrum of Organometallic Compounds $[\text{Fe}_3\text{O}(\text{OOCCH}_2\text{C}_6\text{H}_5)_6(\text{H}_2\text{O})_3](\text{NO}_3)\cdot n\text{H}_2\text{O}$

Table 1. Wavenumbers data of organometallic compounds $[\text{Fe}_3\text{O}(\text{OOCCH}_2\text{C}_6\text{H}_5)_6(\text{H}_2\text{O})_3](\text{NO}_3)\cdot n\text{H}_2\text{O}$

Wavenumber (cm ⁻¹)	Functional groups
3410.1	ν(O-H)
3070.6	ν (Ar-H)
1419.6- 1612.4	ν (C-H),ν (C-O),(C-C)
709.8	ν (N-O)
469.0	ν (Fe-O)

Figure 1. shows the peaks of functional groups of organometallic compounds appearing at wavenumbers 400-4000 cm⁻¹. The main peaks of the organometallic compound appear at the 469 cm⁻¹ for Fe-O vibration (Hasegawa et al, 2007). At the wavenumber 709.8 cm⁻¹ for the N-O vibration as the counter ion of the benzoate ligand. $[\text{Fe}_3\text{O}(\text{OOCCH}_2\text{C}_6\text{H}_5)_6(\text{H}_2\text{O})_3](\text{NO}_3)\cdot n\text{H}_2\text{O}$ has a C-H vibration, the C-O vibration,

and the C-H vibration, which appears at the wavenumbers 1419.6 cm⁻¹, 1612.4 cm⁻¹ (Lesbani et al, 2008). Wavenumber 3070.6 cm⁻¹ is indicated for Ar-H bend vibration. The absorption band at 1689.6 cm⁻¹ for O-H vibration indicating the presence of water ligands in organometallic compounds, which has also strongly appeared by vibration at 3410.1 cm⁻¹. The data of wavenumbers of organometallic compounds $[\text{Fe}_3\text{O}(\text{OOCCH}_2\text{C}_6\text{H}_5)_6(\text{H}_2\text{O})_3](\text{NO}_3)\cdot n\text{H}_2\text{O}$ are summarized in Table 1.

Identification of Natural Bentonite and Bentonite Intercalated Organometallic Compounds $[\text{Fe}_3\text{O}(\text{OOCCH}_2\text{C}_6\text{H}_5)_6(\text{H}_2\text{O})_3](\text{NO}_3)\cdot n\text{H}_2\text{O}$ using FT-IR Spectrophotometer

Before the intercalation process, natural bentonite was characterized using FT-IR spectrophotometer aimed at identifying functional groups. FT-IR spectra of natural bentonite at Figure 2(A) shows vibration of Al-OH-Al vibration in wavenumber 3626.1 cm⁻¹ and vibration of Al-OH-Al at wavenumber 910.4 cm⁻¹. The water content that acts as an interlayer molecule on bentonite appears as a stretch vibration of H-O-H observed at the wavenumber 3448.7 cm⁻¹ while the H-O-H bend vibration appears at 1635.6 cm⁻¹. The absorption at 1033.8 cm⁻¹ indicate the bend vibration of Si-O-Si (Derrick et al, 1999).

There are two stages to remove impurities on bentonite i.e. heating at 400°C and acidification using sulfuric acid (H₂SO₄). On bentonite with heating at 400°C causes a change in deformation of the H₂O bond, since the existing H₂O is released, therefore the bentonite peak becomes widened and expanded so that it eventually collapses at 400°C. The success of this process are characterized by changes in functional groups with the shift in the wavenumbers as seen in Figure 2 (B). The absorption bands in Figure 2 (B) of the Al-OH-Al vibration are shifted at 3695.6 cm⁻¹ and quartz minerals are shifted at 694.3 cm⁻¹ wavenumbers. Vibration of stretch and bend of H-O-H appear on the same wavenumber in natural bentonite, ie at 3448.7 cm⁻¹ and at 1635.6 cm⁻¹. The stretching and bending vibration of Si-O-Si are shown in the 1033.8 cm⁻¹ and 532 cm⁻¹ and the Al-OH-Al bending vibrations remain at the 910.4 cm⁻¹. The second activation process of natural bentonite is acidification using sulfuric acid. Acidification using sulfuric acid aims to remove small metals as impurities attached to bentonite. This activation will open interlayer of bentonite. FT-IR spectrum in Figure 2 (C) shows the shift of wavenumbers of bentonite after acid activation. The absorption band for Al-OH-Al stretching vibration shifts to wavenumber 3672.4 cm⁻¹. The H-O-H stretching vibration shifts to wavenumber 3425.5 cm⁻¹ and the Si-O-Si stretching vibration stay at the wavenumber 1041.5 cm⁻¹. The bending vibrations of Al-OH-Al appearing at 910.4 cm⁻¹ and the H-O-H bending vibrations appear at 1635.6 cm⁻¹. Similar to natural bentonite and bentonite heating at 400°C there is no shift in wavenumbers, stretching and bending vibrations of Si-O-Si stay at wavenumber 532 cm⁻¹.

Intercalation process of bentonite with organometallic compound was completely conducted by adding water to bentonite which is continued with addition of sodium oxide (NaOH). This goal is to build a suspension for easy intercalation process. In the process of intercalation, there is no contact of oxygen from the air, which has protected by introducing N₂ gas. The process of intercalation of bentonite with these

organometallic compounds is carried out by varying the weight ratio, between the weight of the bentonite and the organometallic weight : (1: 1), (1: 2), (1: 3) and (1: 4). This experiment was carried out in order to know the optimum intercalation process.

The results of intercalation of organometallic compounds with the weight ratio of (1: 1), (1: 2), (1: 3) and (1: 4) were characterized using FT-IR spectrophotometer to see functional groups formed as in Figure 3. In Figure 3 (D), it is seen that the vibration of the Fe-O organometallic compound appears at a wavenumber of 462.5 cm⁻¹. The strong of absorption bands for Al-OH-Al stretch vibrations shifted to 3618.4 cm⁻¹. The O-H stretching vibration widened at 3448.7 cm⁻¹. This indicates the presence of an O-H group on benzoate as well as a benzoate ligand in the form of C-C vibration, C = C vibration, C = O vibration appearing at wavenumbers 1388.7 - 1635 cm⁻¹. Si-O-Si stretch vibration at wavenumber 1018.4 cm⁻¹ and Al-OH-Al bending vibrations that appear on wavenumbers 910.4. Stretching and bending vibrations of Al-O-Si are seen at 524.6 cm⁻¹.

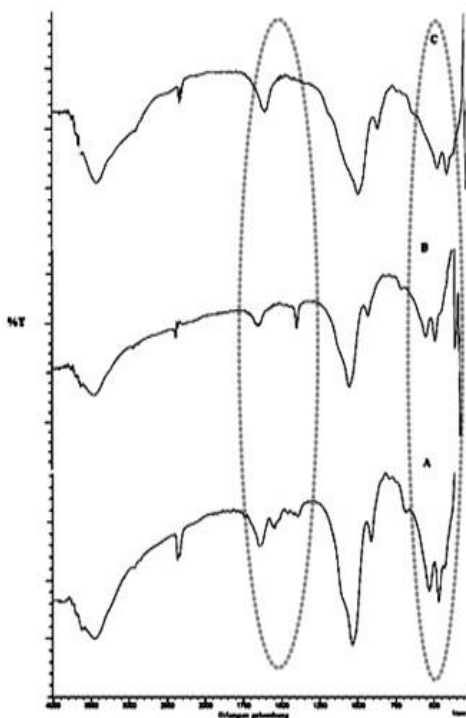


Figure 2. FT-IR spectrum of A) natural bentonite. B) bentonite with heating at 400 °C C) bentonite with acidification

In the result of bentonite intercalation of organometallic compound in Figure 3 (E) (1: 2) it is seen that the vibration of Fe-O organometallic compound appears at wavenumber 470.6 cm⁻¹. The emergence of absorbing bands for the vibration of the Al-OH-Al strain shifted at the wavenumber 3618.4 cm⁻¹. The OH vibration widened at 3448.7 cm⁻¹, the vibration of the C-C, the vibration of C = C, the vibration C = O at 1388.7 - 1635 cm⁻¹ and vibration of Si-O-Si strain at 1033.8 cm⁻¹. Al-OH-Al buckling vibrations that appear at the 910.4 cm⁻¹. Stretching and bending vibrations of Al-O-Si are appeared at 532.3 cm⁻¹

In the result of bentonite intercalation of organometallic compound Figure 3 (F) (1: 3) it is appeared that the emergence of strong absorption at wavenumber 470,6 cm⁻¹ for vibration of Fe-O organometallic compound. The presence of absorbing bands for the OH vibration is widened in the wavenumber 3448.7 cm⁻¹. The vibration of the C-C, the vibration of C = C, the vibration C = O occurs at the wavenumbers 1388.7 – 1635 cm⁻¹, Si-O-Si at 1033.8 cm⁻¹. Al-OH-Al buckling vibrations that appear at 910.4 cm⁻¹ wavenumbers, whereas, stretching vibration of Al-O-Si bends are appeared at 524.6 cm⁻¹. These vibrations are almost similar with vibration in Figure 3G.

The FT-IR spectra of Figure 3 show that the variation in the weight ratio of intercalated bentonite did not differ significantly. In order to know the optimal intercalation process, characterization using XRD was conducted for further analysis.

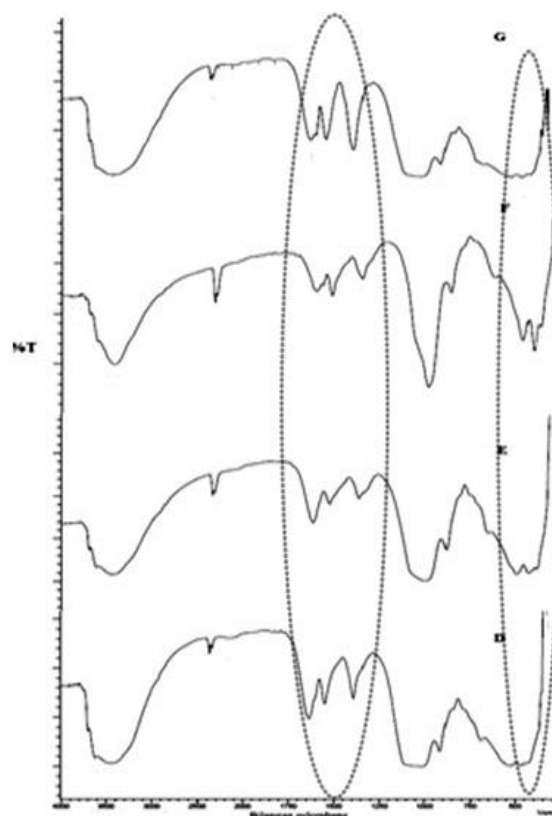


Figure 3. FT-IR spectrum of Intecalated Bentonite, D) 1:1, E) 1:2, F) 1:3, G) 1:4.

Identification of Natural Bentonite and Bentonite Intercalated Organometallic Compounds [Fe₃O(OOCC₆H₅)₆(H₂O)₃] (NO₃)·nH₂O using X-Ray Diffraction

The objectives analysis using XRD is to look at the structural changes that occur in bentonite after intercalation by observing the diffraction angle change (2θ). Bentonite is a class of minerals that contain montmorillonite as main fraction. (Brindley et al, 1990). Bentonite shows the observed montmorillonite at 2θ from 3 - 6°. This is evident from the diffraction angle (2θ) of natural bentonite, bentonite with heating at 400°C and bentonite with acidification using sulfuric acid ie the shifting angle of motnmorillonite diffraction at 4.1°, 3.3° and 4.1°.

The existence of diffraction at the 2θ angle of 20° and 26° as shown in Figure 4 (A), (B), and (C) indicates the existence of

other minerals ie quartz and illite. If bentonite is intercalated by molecules and compounds, there will be XRD diffraction patterns shift of montmorillonite, quartz, and illite (Bertella et al., 2011). In Figure 4 (D) shows the weight ratio (1: 1), there is a shift in the diffraction angle of 2θ montmoriloite in bentonite of 5.2° with basal spacing of 16.7 Å.

In comparison (1: 2) presented in Figure 4 (E) also seen shift angle diffraction 2θ montmoriloit at 5.3° with basal spacing 16.4 Å. In Figure 4 (F), the ratio (1: 3) also shows a shift in the angle of diffraction of 2θ montmoriloite at bentonite of 5.2° with basal spasing of 16.8 Å. The shift of the diffraction angle 2θ in the ratio of the weight of bentonite to the organometallic compound [Fe₃O(OOCC₆H₅)₆(H₂O)₃](NO₃)·nH₂O can be seen in Figure 4 (D), (E), (F), and (G).

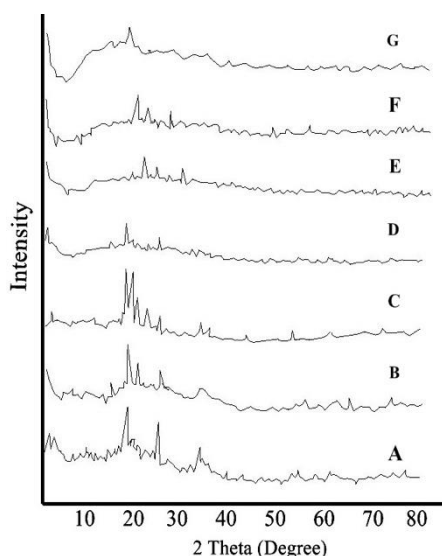


Figure 4 Diffraction patterns of A) natural bentonite, B) bentonite with heating at 400 °C C) bentonite with acidification D) bentonit:organometallic 1:1, E) 1:2, F) 1:3, and G) 1:4.

In the ratio (1: 4) shown in Figure 4 (G) it does not have a 2θ montmorillonite diffraction angle shift in bentonite but has a basal spacing of 24 Å. This can not be said to be optimal because there is no shift in the diffraction angles of 2θ montmorillonite. The success of bentonite intercalation of organometallic compounds can be seen from the shifting angle of diffraction of 2θ montmorillonite from 3 - 6°. In Figure 4 (G) the entry of organometallic compound is not only in 1 layer, but in other layers as well.

Therefore, the results of the XRD characterization data can be stated that in the weight ratio of bentonite: organometallic compound (1: 3) is more optimally intercalated. To be able to demonstrate the optimal intercalation results, another process of characterization was conducted using XRF analysis (X-ray Fluorescence).

Identification of Natural Bentonite and Bentonite Intercalated Organometallic Compounds [Fe₃O(OOCC₆H₅)₆(H₂O)₃](NO₃)·nH₂O using X-Ray Fluorescence Sinar-X (XRF)

Characterization using XRF aims to look at the metal oxide compositions contained in natural bentonite, activated bentonite and intercalated bentonite with organometallic compound in the

ratio (1: 1), (1: 2), (1: 3) and (1: 4). The results data of XRF analysis is presented in Table 3. In Table 3 it is seen that natural bentonite is composed of montmorillonite mineral containing silica and alumina which yield percentage amount of Al₂O₃ and SiO₂ metal oxides of 17% and 43.6%. Other measured metal oxides are P₂O₅ with a percentage of 0.71%, K₂O with a percentage of 0.2%. Composition of CaO with percentage as much as 0.99%, TiO₂ with percentage 1.87%, V₂O₅ with percentage 0.11%, Cr₂O₃ with percentage 33.39%, NiO with percentage 0.87%, CuO with percentage 0.15% ZnO with a percentage of 0.09%, Re₂O₇ with 0.11% percentage, and Eu₂O₃ with 0.2%.

With the activation of natural bentonite causes the value of metal oxide content decreases. This is in accordance with the activation purpose of removing impurities on bentonite in the form of small metals. Activation of the first bentonite by heating at 400°C indicates that some oxides are decreased, as CaO decreases its percentage to 0.92%, V₂O₅ to 0.07%. While other metal oxides have the same percentage as natural bentonite despite the presence of binding metal oxides, such as TiO₂ to 1.91%, Cr₂O₃ to 0.11%, Mn to 0.19%, Fe₂O₃ to 33.57%. This reduction in metal oxide content due to metal oxides on the bentonite is already lost oxide activation due to heating to form other inorganic substances.

Table 2. Metal oxide composition using XRF

Sampeal	Al ₂ O ₃ (%)	SiO ₂ (%)	Fe ₂ O ₃ (%)	P ₂ O ₅ (%)	K ₂ O (%)	CaO (%)	TiO ₂ (%)	V ₂ O ₅ (%)	Cr ₂ O ₃ (%)	MnO (%)
BA0	17	43,6	33,57	0,71	0,2	0,997	1,87	0,11	0,075	0,12
B400	17	43,7	33,57	0,7	0,21	0,92	1,91	0,074	0,11	0,19
BAA	11	28,8	29,2	-	0,19	0,94	1,73	0,062	0,068	0,17
HA1	10	29,7	55,22	0,67	-	0,67	1,41	0,063	0,088	0,13
HB2	8,2	23,9	63,89	0,43	0,101	0,57	1,06	0,03	0,095	0,11
HC3	6,2	18,7	71,75	0,42	0,084	0,084	0,815	0,03	0,100	0,089
HD4	6,1	19	70,12	0,45	0,084	0,35	0,67	0,02	0,11	0,080

Sampeal	NiO (%)	CuO (%)	P ₂ O ₅ (%)	ZnO (%)	Re ₂ O ₇ (%)	Rb ₂ O (%)	SO ₂ (%)	MgO ₂ (%)	Eu ₂ O ₃ (%)	Re ₂ O ₇ (%)	NiO (%)
BA0	0,899	0,16	0,71	0,08	-	-	-	-	0,2	-	0,899
B400	0,899	0,16	0,7	0,08	0,1	-	-	-	-	0,1	0,899
BAA	0,882	0,15	-	0,080	0,1	-	17	9,6	-	0,1	0,882
HA1	1,03	0,16	0,67	-	-	-	-	-	-	-	1,03
HB2	0,945	0,14	0,43	-	-	0,3	-	-	-	-	0,945
HC3	0,93	0,13	0,42	-	-	0,36	-	-	-	-	0,93
HD4	0,82	0,13	0,45	-	-	0,37	-	-	-	-	0,82

BAO: natural bentonite ; B400: physical activation at 400 °C; BAA: chemical activation using sulfuric acid; HA1: (1:1); HB2: (1:2); HC3: (1:3); HD4: (1:4).

The second activation of natural bentonite by adding sulfuric acid. This causes a decrease in the percentage of metal oxide. The decrease in the percentage of metal oxide on the acidified bentonite is shown in Table 2. The decrease of metal oxide is Al₂O₃ to 11%, SiO₂ to 28.8%, K₂O to 0.19%, TiO₂ to 1.73%, V₂O₅ to 0.06%, Cr₂O₃ becomes 0.06%, Mn to 0.17%, Fe₂O₃ to 29.2%, NiO to 0.88%, and CuO to 0.15%.

Furthermore, to determine the results of intercalation of bentonite with organometallic compound [Fe₃O(OOCC₆H₅)₆(H₂O)₃](NO₃)·nH₂O in the ratio (1: 1), (1: 2), (1: 3) and (1: 4) are performed by observing the oxide content, especially the Al₂O₃ and SiO₂ metal oxides located on the inseminating montmorillonite layer. Then the intercalation compound content of organometallic compound causes the metal oxide of Fe₂O₃ to increase. The result of XRF analysis in Table 2 shows that the ratio of weight (1: 2) and (1: 3) has significant decrease of Al₂O₃, Al₂O₃ has a percentage of 8.2%,

SiO₂ has a percentage of 23.9% and an increase of Fe₂O₃ to 63, 89%.

However, in the weight ratio (1: 3) the metal oxide decreased Al₂O₃ to 6.2%, SiO₂ had a percentage of 18.7% and the increase of Fe₂O₃ to 71.75%. Therefore, the result of bentonite intercalation of the optimal organometallic compound is shown in the ratio (1: 3) because it contains a lot of Fe₂O₃ composition as well as decreasing the good percentage of each treatment.

CONCLUSION

Bentonite intercalated organometallic compounds [Fe₃O(OOCC₆H₅)₆(H₂O)₃](NO₃) showed optimal intercalation process in the weight ratio (1: 3). Characterization using XRD showed a diffraction at 5.2 ° having a basal spacing of 16.8 Å. Further characterization using XRF showed the intercalation (1: 3) has percentage 12.75% of metal oxide.

ACKNOWLEDGEMENT

We thank to Prof. Aldes Lesbani for fruitful discussion related with this research. HPU and DMS thanks to Integrated Research Laboratory, Graduate School, Sriwijaya University for laboratory equipment and support.

REFERENCES

- Abderrazek, K., Najoua, F.S. and Srasra, E., 2016. Synthesis and characterization of [Zn–Al] LDH: Study of the effect of calcination on the photocatalytic activity. *Applied Clay Science*, 119, 229–235.
- Bertella, F. and Pergher, S.B.C., 2015. Pillaring of bentonite clay with Al and Co. *Microporous and Mesoporous Materials*, 2011, 116–123
- Brindley, W., and Brown, G. (1980). *Crystal Structure of Clay Minerals and their X Ray Identification*, Mineralogical Society, London.
- Derrick, M, R., Szubik, D, and Landry, J M., 1999. Infrared Spectroscopy Conservation Science. The Getty Conservation Institute. Los Angeles.
- Ding, M., Zuo, S. and Qi, C., 2015. Preparation and characterization of novel composite AlCr-pillared clays and preliminary investigation for benzene adsorption. *Applied Clay Science*, 115, 9–16.
- Gil, A., Assis, F.C.C., Albeniz, S., and Korili, S.A., 2011. Removal of dyes from wastewaters by adsorption on pillared clays. *Chemical Engineering Journal*, 168(3), 1032–1040.
- Hasegawa, T., Fernanda F. M., David J. E. S., and Nunes., 2007. A new capped iron(III) trinuclear benzoate cluster. *Journal of Coordination Chemistry*. 60(2), 185–191.
- Lesbani, A., Kawamoto, R., Uchida, S., and Mizuno, N., 2008. Control of structures and sorption properties of ionic crystals of A₂[Cr₃O(OOCC₂H₅)₆(H₂O)₃]₂[α-SiW₁₂O₄₀] (A = Na, K, Rb, NH₄, Cs, TMA). *Inorganic chemistry*, 47(8), 3349–57.
- Ozcan, A., Omeroglu, C., Erdogan, Y., and Ozcan, A, S. 2007. Modification of Bentonite with A Cationic Surfactant; An Adsorption Study of Textile Dye Reactive Blue 19. *Journal of Hazardous*. 140; 173-179.
- Ozcan, S, A., and Ozcan, A. 2004. Adsorption of Acid Dyes from Aqueous Solutions onto Acid-Activated Bentonite. *Journal of Colloid and Interface Science*. 276: 39-46.
- Santos, S.C.R., Oliveira, Á.F.M. and Boaventura, R.A.R., 2016. Bentonitic clay as adsorbent for the decolourisation of dyehouse effluents. *Journal of Cleaner Production*, 126, 667–676.
- Scoonheydt, R.A., Pinnavaia, T., Lagaly, G., and Ganga, N. 1999. *Pillared Clays and Pillared Layered Solids*. Belgium.
- Szafran, Z., Pike, R.M., Singh, M.M. 1991. *Microscale Inorganic Chemistry: A Comprehensive Laboratory Experience*, Wiley.
- Uchida, S., Lesbani, A., Ogasawara, Y., and Mizuno, N., 2012. Ionic Crystals [M₃O(OOCC₆H₅)₆(H₂O)₃]₄[α-SiW₁₂O₄₀] (M = Cr, Fe) as Heterogeneous Catalysts for Pinacol Rearrangement. *Inorganic Chemistry*, 51(2), 775–777.
- Yang, R.T., 1999, Structural Aspects of Metal Oxide Pillared Sheet Silicates, *J. Chem. Soc. Faraday Trans*
- Zhu, H., M and Vansant, E.E., 2008. Correlation Between The Micropore Structure and The Adsorption of Benzene in Pillared Clays, Separation Technology. *Amsterdam*. 466: 153-158.